

Superconductivity in MgB_2 and TaB_2 : A Full-Potential Electronic Structure Comparison

Prabhakar P. Singh

Department of Physics, Indian Institute of Technology, Powai, Mumbai -400076, India
(February 1, 2008)

We present a comparison of electronic structure of MgB_2 and TaB_2 , the two new superconductors, as well as VB_2 , calculated using full-potential, density-functional-based methods in $P6/mmm$ crystal structure. Our results, described in terms of (i) density of states (DOS), (ii) band-structure, and (iii) the DOS and the electronic charge density in a small energy window around the Fermi energy E_F . In particular, the charge density around E_F in MgB_2 and TaB_2 show striking similarity as far as the B plane is concerned. A comparison of their band-structures, coupled with l -character analysis, indicates that TaB_2 has substantially more p -character than VB_2 along $A-L$ and $H-A$ directions near E_F .

With the discovery of superconductivity in MgB_2 [1], many Boron compounds such as BeB_2 , LiB_2 , AlB_2 [2] and transition-metal borides [3–5] with AlB_2 -structure are being reexamined for possible superconductivity. The search for new MgB_2 -like superconductors is motivated not only by the desire to discover new superconductors but also with the hope that it will be helpful in unravelling the nature of interaction responsible for superconductivity in these materials. In this context, the recently reported superconductivity in TaB_2 [4] with a superconducting transition temperature $T_c \approx 9.5K$, if confirmed [4,5], may lead to a better understanding of superconductivity in MgB_2 and MgB_2 -like superconductors such as TaB_2 .

The continuing experimental [6–8] and theoretical [9–13] efforts at characterizing and understanding the nature of superconductivity in MgB_2 have made substantial progress. However, a complete understanding of superconductivity in MgB_2 , and for that matter in TaB_2 , is still lacking. It is interesting to note that the superconducting transition temperatures in MgB_2 and TaB_2 are $39K$ and $9.5K$, respectively, while VB_2 has been found not to superconduct down to $0.42K$ [3,4]. Thus a theoretical study of those aspects of electronic structure of MgB_2 , TaB_2 and VB_2 , which could be responsible for superconductivity or lack thereof in these materials, may provide some clues as to why TaB_2 is superconducting but VB_2 is not. This, in turn, may improve our understanding of superconductivity in MgB_2 itself.

In this paper we present a full-potential electronic structure study of TaB_2 and VB_2 in $P6/mmm$ crystal structure using density-functional-based methods. For comparison with MgB_2 , we use our fully-relaxed, full-potential electronic structure results for MgB_2 in $P6/mmm$ crystal structure [13]. We analyze our results in terms of (i) density of states (DOS), (ii) band-structure along symmetry directions, and (iii) the DOS and the electronic charge density in a small energy window around the Fermi energy, E_F , in these systems.

We have used our own full-potential program as well as LMTART package [14] to calculate, self-consistently, the electronic structure of TaB_2 and VB_2 using the experimental lattice constants. These calculations have been used to study the band-structure along symmetry directions and site- and symmetry-decomposed densities of states. For studying the charge density in a small energy window around E_F we have used the Stuttgart TB LMTO package [15]. The fully-relaxed, full-potential electronic structure of MgB_2 was calculated as described in Ref. [13]

Based on our calculations, described below, we find that in TaB_2 , within a small energy window around E_F , the charge density in the B plane is still two-dimensional and it is associated with the $p_{x,y}$ orbitals as is the case for MgB_2 [10,11,13]. The corresponding charge density in VB_2 does not have this character. A comparison of band-structures of MgB_2 , TaB_2 and VB_2 along symmetry directions reveals that the Γ_5 point is well below E_F in both TaB_2 and VB_2 . However, based on our understanding of superconductivity in MgB_2 [9–13], we find that the 7-th band, specially around K and A points with substantially more p -character in TaB_2 than in VB_2 , may play an important role in making TaB_2 a superconductor.

Before describing our results in detail, we provide some of the computational details of our calculations. The charge self-consistent full-potential LMTO calculations were carried out with the generalized gradient approximation for exchange-correlation of Perdew *et al.* [16] and 484 k -points in the irreducible wedge of the Brillouin zone. The basis set used consisted of s , p , d and f orbitals at the Ta (V) site and s , p and d orbitals at the B site. The potential and the wavefunctions were expanded up to $l_{max} = 6$. The input to the tight-binding LMTO calculations, carried to charge self-consistency, were similar to that of the full-potential calculations except for using spherically symmetric potential and the space-filling atomic spheres.

In Table I we give the lattice constants used for calculating the electronic structure of MgB_2 , TaB_2 and VB_2 . Note that the lattice constants for TaB_2 and VB_2 are taken from experiments [4], while that for MgB_2 are obtained theoretically as described in Ref. [13]. In Table I we also show the calculated plasma frequencies and the total density of states per spin, $n(E_F)$, at E_F for these compounds.

	a (a.u.)	c (a.u.)	ω_p^x (eV)	ω_p^z (eV)	$n(E_F)$
MgB_2	5.76 (5.834)	6.59 (6.657)	7.04	6.77	4.70
TaB_2	5.826	1.0522	9.01	9.71	6.57
VB_2	5.665	1.0196	5.62	6.60	9.24

We show in Fig. 1 the total density of states for MgB_2 , TaB_2 and VB_2 calculated using the full-potential LMTO method at the lattice constants given in Table I. The gross features of the DOS of TaB_2 and VB_2 are similar if one takes into account the differences arising out of the change in the d -bandwidth as one goes from V to Ta . The comparison with MgB_2 must be done keeping in mind the differences in the atomic electronic configurations between Mg ($3s^2$) and Ta ($5d^36s^2$) and V ($3d^34s^2$). As a result the d -DOS at E_F changes from 0.9 st/Ry at the Mg site to 8.8 st/Ry at the Ta site, and finally to 16.8 st/Ry at the V site in the respective diborides. More importantly, we find that the p -DOS at the B site in MgB_2 , TaB_2 and VB_2 decreases steadily from 3.36 st/Ry in MgB_2 to 1.55 st/Ry in TaB_2 and to 0.58 st/Ry in VB_2 . The decrease in the availability of p -electrons around E_F may result in the decrease of T_c in TaB_2 and no superconductivity in VB_2 . The DOS of TaB_2 compares reasonably well with the cluster calculations of [17], however, the location of E_F is clearly different.

In the conventional, BCS-type superconductors the DOS within an interval of $\pm\hbar\omega_D$ ($\omega_D \equiv$ Debye frequency) at E_F is crucial for superconductivity. Since the B partial DOS is more relevant for superconductivity in the diborides, we have plotted in Fig. 2 the symmetry-decomposed DOS at the B site within a small energy interval around E_F in MgB_2 , TaB_2 and VB_2 . From Fig. 2 we find that in TaB_2 the DOS at E_F with x (y) symmetry is half of the corresponding DOS in MgB_2 , while in VB_2 it is more than a factor of four less than in MgB_2 . Since the electrons in the B plane are expected to play a crucial role in determining superconducting properties, it is not surprising to find significant differences in the DOS with x (y) symmetry in MgB_2 , TaB_2 and VB_2 .

To study the differences in the band-structures of MgB_2 and the transition metal diborides as well as between TaB_2 and VB_2 , in Fig. 3 we have plotted the band-structures along the symmetry directions for TaB_2 and VB_2 . The presence of d -electrons in the transition metal diborides implies more d -like bands below E_F in comparison to MgB_2 . As a result, the Γ_5 point is well below E_F in both TaB_2 and VB_2 . However, the 7-th

band at K point, with significant p_z character, in TaB_2 is below E_F while it is above E_F in VB_2 . Our l -character analysis also shows that the 7-th band, which crosses E_F along $A-L$ and $H-A$ directions, has substantial p_x and p_z characters in TaB_2 but only a very small p character in VB_2 . Based on our understanding of superconductivity in MgB_2 [9,10], it seems reasonable to state that the 7-th band, specially around K and A points, may play an important role in making TaB_2 a superconductor.

To further illustrate the differences between MgB_2 , TaB_2 and VB_2 , we have calculated their electronic charge densities within a 5 mRy energy window around E_F using the TB LMTO method with the lattice constants as given in Table I. In these calculations the atomic sphere radii were adjusted to minimize the discontinuity in the Hartree potential across the atomic spheres which have been found to give reliable results [18]. In Fig. 4, we show the charge density calculated within a 5 mRy energy window around E_F for TaB_2 and VB_2 . By comparing the charge density of TaB_2 with that of MgB_2 as given in Ref. [13], we find that to some extent the two-dimensional character of the charge density due to $p_{x,y}$ orbitals in the B plane remains intact in TaB_2 . In VB_2 , however, the decrease in the lattice constants a and c has completely destroyed the two-dimensional nature of the charge density in the B plane. These differences may account for no superconductivity in VB_2 .

In conclusion, we have presented the results of our full-potential electronic structure calculations for MgB_2 , TaB_2 and VB_2 in $P6/mmm$ crystal structure using density-functional-based methods. We have analyzed our results in terms of the density of states, band-structure along symmetry directions, and the DOS and the electronic charge density in a small energy window around the Fermi energy in these systems. In TaB_2 , we find that within a small energy window around E_F , the charge density in the B plane is still two-dimensional and it is associated with the $p_{x,y}$ orbitals as is the case for MgB_2 . The corresponding charge density in VB_2 does not have this character. By comparing their band-structures we find that the 7-th band, specially around K and A points with substantially more p -character in TaB_2 than in VB_2 , may play an important role in making TaB_2 a superconductor.

The author would like to thank A. V. Mahajan for helpful discussions.

-
- [1] J. Akimitsu, Symp. on Transition Metal Oxides, Sendai, January 10, 2001; J. Nagamatsu, *et al.*, Nature **410**, 63 (2001).
 - [2] I. Felner, cond-mat/0102508; D. P. Young *et al.*, cond-mat/0104063.

- [3] L. Layarowska and E. Layarovski, J. Less Common Met. **67**, 249 (1979).
- [4] D. Kaczorowski *et al.*, cond-mat/0103571; D. Kaczorowski *et al.*, cond-mat/0104479.
- [5] V. A. Gasparov *et al.*, cond-mat/0104323.
- [6] S. L. Bud'ko *et al.*, Phys. Rev. Lett. **86**, 1877 (2001).
- [7] H. Schmidt *et al.*, cond-mat/0102389; G. Karapetrov *et al.*, cond-mat/0102312.
- [8] Tsuda *et al.*, cond-mat/0104489.
- [9] J. E. Hirsch, cond-mat/0102115; J. M. An and W. E. Pickett, cond-mat/0102391.
- [10] J. Kortus *et al.*, cond-mat/0101446; K. D. Belashchenko *et al.*, cond-mat/0102290.
- [11] G. Satta *et al.*, cond-mat/0102358; Y. Kong *et al.*, cond-mat/0102499.
- [12] A. Y. Liu *et al.*, cond-mat/0103570.
- [13] Prabhakar P. Singh, Submitted to Phys. Rev. Lett.
- [14] S. Y. Savrasov, Phys. Rev. B **54**, 16470 (1996).
- [15] The Stuttgart TB LMTO 4.7 package.
- [16] J. P. Perdew and Y. Wang, Phys. Rev. B **45**, 13244 (1992); J. Perdew *et al.*, Phys. Rev. Lett. **77**, 3865 (1996).
- [17] H. Kawanowa *et al.*, Phys. Rev. B **60**, 2855 (1999).
- [18] Prabhakar P. Singh and A. Gonis, Phys. Rev. B **49**, 1642 (1994).

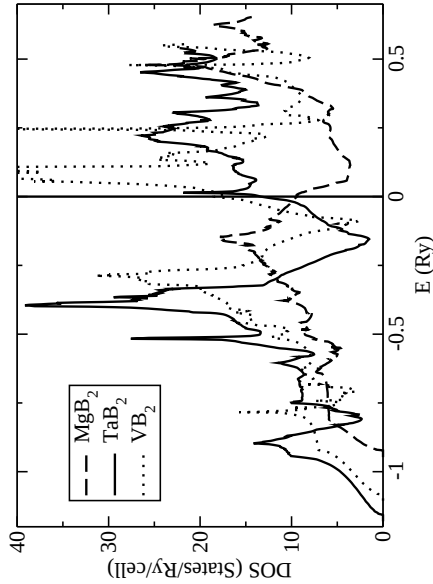


FIG. 1. The total density of states calculated at the lattice constants as given in Table I using the full-potential LMTO method.

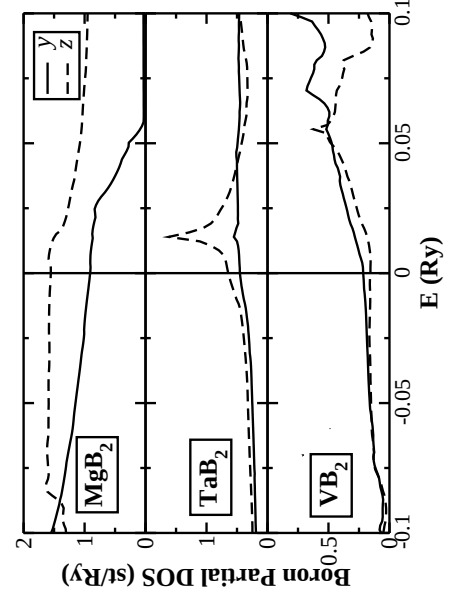


FIG. 2. The partial B density of states around Fermi energy calculated at the lattice constants as given in Table I using the full-potential LMTO method.

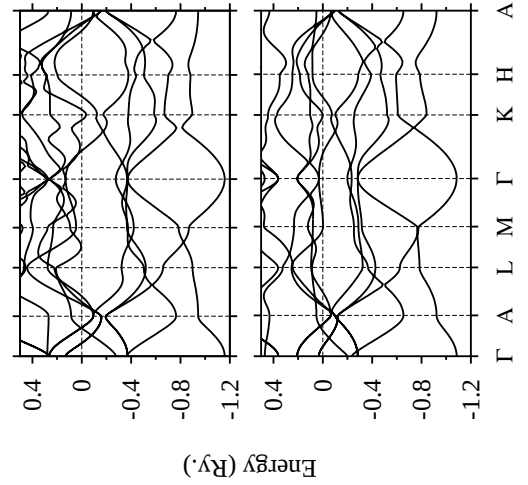


FIG. 3. The band-structure along symmetry directions calculated at the lattice constants as given in Table I using the full-potential LMTO method.



FIG. 4. The isosurfaces of charge density within a 5 mRy energy window around the Fermi energy in the primitive cell of TaB_2 (left) and VB_2 (right), calculated at the lattice constants as given in Table I using the TB LMTO method. The values of the isosurfaces (8,6,4,2,1) decrease as one moves away from the B plane. The unit for charge density in the volume is $10^{-4}[e/(a.u.)^3]$ and the view is off-diagonal at an angle of 30° .